

RAPID COMMUNICATION

Nodal superconducting gap in LiFeP revealed by NMR: Contrast with LiFeAs*

To cite this article: A F Fang *et al* 2021 *Chinese Phys. B* **30** 047403

View the [article online](#) for updates and enhancements.

You may also like

- [Absence of strong magnetic fluctuations in FeP-based systems LaFePO and Sr_{1-x}Sc_xO₃FeP](#)
A E Taylor, R A Ewings, T G Perring *et al.*
- [Molecular beam epitaxy growth of superconducting LiFeAs film on SrTiO₃\(001\) substrate](#)
K. Chang, P. Deng, T. Zhang *et al.*
- [³¹P NMR investigation of the superconductor LiFeP \(T_c = 5 K\)](#)
Huiyuan Man, Shengli Guo, Guoxiang Zhi *et al.*

Nodal superconducting gap in LiFeP revealed by NMR: Contrast with LiFeAs*

A F Fang(房爱芳)¹, R Zhou(周睿)^{2,3,†}, H Tukada⁴, J Yang(杨杰)², Z Deng(邓正)², X C Wang(望贤成)², C Q Jin(靳常青)², and Guo-Qing Zheng(郑国庆)^{2,4}

¹Department of Physics, Beijing Normal University, Beijing 100875, China

²Institute of Physics, Chinese Academy of Sciences, and Beijing National Laboratory for Condensed Matter Physics, Beijing 100190, China

³Songshan Lake Materials Laboratory, Dongguan 523808, China

⁴Department of Physics, Okayama University, Okayama 700-8530, Japan

(Received 10 January 2021; revised manuscript received 5 February 2021; accepted manuscript online 5 March 2021)

Identifying the uniqueness of FeP-based superconductors may shed new lights on the mechanism of superconductivity in iron-pnictides. Here, we report nuclear magnetic resonance (NMR) studies on LiFeP and LiFeAs which have the same crystal structure but different pnictogen atoms. The NMR spectrum is sensitive to inhomogeneous magnetic fields in the vortex state and can provide the information on the superconducting pairing symmetry through the temperature dependence of London penetration depth λ_L . We find that λ_L saturates below $T \sim 0.2 T_c$ in LiFeAs, where T_c is the superconducting transition temperature, indicating nodeless superconducting gaps. Furthermore, by using a two-gaps model, we simulate the temperature dependence of λ_L and obtain the superconducting gaps of LiFeAs, as $\Delta_1 = 1.2 k_B T_c$ and $\Delta_2 = 2.8 k_B T_c$, in agreement with previous result from spin-lattice relaxation. For LiFeP, in contrast, λ_L does not show any saturation down to $T \sim 0.03 T_c$, indicating nodes in the superconducting gap function. Finally, we demonstrate that strong spin fluctuations with diffusive characteristics exist in LiFeP, as in some cuprate high temperature superconductors.

Keywords: iron-based superconductor, nuclear magnetic resonance, superconducting pairing symmetry, spin fluctuations

PACS: 74.70.Xa, 74.25.nj, 74.20.Rp, 75.40.Gb

DOI: 10.1088/1674-1056/abec37

1. Introduction

As the second class of high-temperature superconductors, iron-based superconductors were discovered more than one decade ago.^[1] But its superconducting pairing mechanism is still unclear. The phase diagram of iron-pnictides is very similar to that of the cuprates high-temperature superconductor family.^[2] Antiferromagnetism and nematic orders exist around the superconducting dome and both compete with superconductivity in these two families.^[3] Therefore both spin and nematic fluctuations are suggested to be candidates for the glue of the superconducting pairing.^[4] Although, the symmetry of the superconducting gap in cuprates is believed to be d-wave,^[5,6] the situation is more complicated for iron-pnictides. Firstly, there are multiple superconducting gaps as first evidenced by the spin-lattice relaxation rate and the Knight shift,^[7] instead of a single superconducting energy gap in cuprates. Secondly, the gap symmetry is different in different iron-based families. In FeAs-based superconductors, the superconducting gap is found to be isotropic and fully-opened.^[8–11] But for P-doped BaFe₂As₂ which is equivalently doped, previous studies suggest the existence of nodes

in the superconducting gaps.^[12,13] If As is completely substituted by P, the pnictogen height above the iron plane will become smaller, which is suggested to be an important factor in the theory based on spin fluctuations.^[14] Therefore, clarifying the uniqueness of FeP-based superconductor can shed lights on the mechanism of superconducting pairing in iron-pnictides.

LiFeP is a superconducting material with transition temperature $T_c \sim 4.2$ K.^[15] Its crystal structure is identical to that of LiFeAs ($T_c \sim 18$ K),^[16] but the height of the P site is much lower than that of As. Previous tunnel diode oscillator (TDO) measurements found that the London penetration depth shows a flat temperature dependence in LiFeAs but a linear temperature dependence in LiFeP, suggesting nodeless and nodal superconducting gaps, respectively.^[17] However, TDO measurement is only sensitive to the change of penetration depth on the surface of the sample which can be affected by disorder or lattice distortion from the surface. Until now, no bulk measurement on λ_L has been done. NMR spectrum is sensitive to inhomogeneous magnetic fields in the vortex state, from which λ_L of the bulk sample can be directly deduced.^[18,19] Besides the properties of the superconducting state, the electron correlations in the normal state of LiFeP are also of inter-

*Project supported by the National Natural Science Foundation of China (Grant Nos. 11904023, 11974405, 11674377, and 11634015), the Fundamental Research Funds for the Central Universities, China (Grant No. 2018NTST22), the National Key R&D Program of China (Grant Nos. 2016YFA0300502 and 2017YFA0302904), and the Strategic Priority Research Program of the Chinese Academy of Sciences (Grant No. XDB33010100).

†Corresponding author. E-mail: rzhou@iphy.ac.cn

est. In most iron-based superconductors, strong spin fluctuations have been observed,^[11,20–22] and quantum critical point related to the magnetic order is suggested inside the superconducting dome.^[19,23] Unlike these compounds, a previous NMR study at $B_0 = 4.65$ T has suggested that low-energy spin fluctuations are very weak in LiFeP.^[24] However, for spin-lattice relaxation rate $1/T_1$ measurement, the NMR frequency, which is related to the energy of spin fluctuations, can play an important role. Therefore, $1/T_1$ measurements at different fields are needed in order to investigate intrinsic spin fluctuations.

In this work, we investigate the superconducting gap symmetry of LiFeP and LiFeAs by detailed NMR studies of London penetration depth λ_L . Nodal superconductivity is revealed in LiFeP while LiFeAs is found to be a nodeless superconductor. For LiFeP, strong spin fluctuations with diffusive characteristics are found by spin-lattice relaxation measurements, which is similar to some cuprate superconductors.

2. Experiment

The LiFeAs single crystal and LiFeP polycrystal samples were grown by the solid-state reaction and the self-flux methods, respectively.^[15,16] The ^{75}As spectra were obtained by integrating the spin echo as a function of frequency at 7.5 T. The ^{31}P -NMR spectra were obtained by fast Fourier transform of the spin echo. The pulse width is only 5 μs in order to cover the full spectrum. The T_1 was measured by using the saturation-recovery method, and obtained by a good fitting of the nuclear magnetization to $1 - M(t) = M_0 e^{-t/T_1}$, where $M(t)$ is the nuclear magnetization at time t after the single saturation pulse and M_0 is the nuclear magnetization at thermal equilibrium.

3. Results and discussion

3.1. London penetration depth in LiFeP: contrast with LiFeAs

Figure 1(a) shows the ^{75}As -NMR central line at various temperatures, which can be well fitted by a single Lorentz function. By cooling down into the superconducting state, the NMR line shifts to lower frequency and broadens almost symmetrically. In the vortex state, the magnetic field B_0 penetrates into a sample in the unit of quantized flux $\phi_0 = 2.07 \times 10^{-15}$ T·m², thus the field becomes inhomogeneous, leading to the observed broadening in Fig. 1(a). The shift of the spectrum is due to the singlet pairing and diamagnetism from the vortex-lattice formation. For $B_{c1} \ll B_0 \ll B_{c2}$, where B_{c1} and B_{c2} are the lower and upper critical fields, respectively, the field distribution ΔB can be written as^[25]

$$\Delta B = 0.0609 \frac{\phi_0}{\lambda_L^2}, \quad (1)$$

which can be detected by the NMR spectrum broadening $\Delta f = \gamma_n \Delta B$, where γ_n is the gyromagnetic ratio. In both normal state and superconducting state, the spectra can be well fitted by a single Lorentz function. Theoretically, the NMR lineshape in the superconducting state should be asymmetric due to inhomogeneous distribution of the magnetic field. However, the shape we observed is rather symmetric, which is in agreement with the previous NMR study on $\text{NaFe}_{1-x}\text{Co}_x\text{As}$.^[18,19] This might be because the vortex-cores have small random displacements from triangular lattice in a 2D layered system when the correlation between different layers is small. Such displacements will broaden the effective core radius and truncate the high-field tail in the field distribution. Then the line will become more symmetric, like the case in $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$.^[26] This can explain why the broadening in LiFeAs is rather symmetric, since iron-based superconductors are also quite 2D.

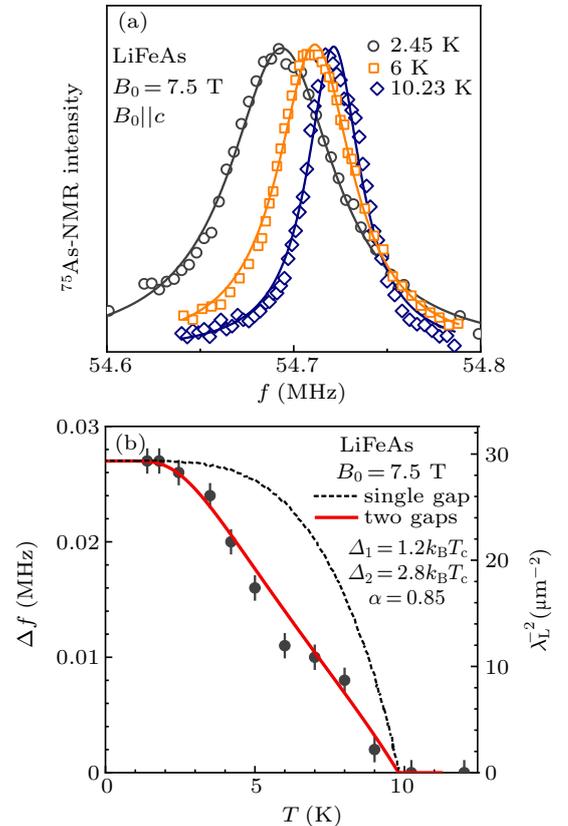


Fig. 1. (a) ^{75}As -NMR spectra of LiFeAs at various temperatures with magnetic field $B_0 = 7.5$ T applied along c -axis. The spectra are fitted by a single Lorentz function. (b) Temperature dependence of the line broadening Δf and London penetration depth λ_L^{-2} of LiFeAs. The black dashed curve represents the variation with temperature expected for a conventional s -wave superconductor.^[27] The red solid curve represents the simulation by the two-gaps model described in the text.

The full width at half maximum (FWHM) of a convolution of two Lorentzian functions is the sum of individual FWHMs, so the broadening can be obtained by simply subtracting the T -independent width above T_c , $\Delta f = \text{FWHM}(T) - \text{FWHM}(T > T_c)$. In Fig. 1(b), we summarize

the temperature dependence of Δf and λ_L^{-2} which start to saturate below $T \sim 0.2T_c$. By using Eq. (1), $\lambda_L(T \rightarrow 0) = 185$ nm is calculated, which is consistent with the result, $\lambda_L = 210$ nm, obtained by small-angle neutron scattering (SANS).^[28] In the London theory, λ_L^{-2} is proportional to the superconducting carrier density n_s as^[29]

$$n_s = \frac{m^* c^2}{4\pi e^2 \lambda_L^2}, \quad (2)$$

where m^* is the effective mass of the carriers. When the superconducting correlation length is much smaller than λ_L , the superconducting carrier density n_s can be expressed as^[29]

$$\tilde{n} = 1 + 2 \int_0^\infty dE \frac{\partial f(E)}{\partial E} \frac{N(E)}{N_0}, \quad (3)$$

where $\tilde{n} = n_s(T)/n_s(0)$, $f(E)$ is the Fermi function, and $N(E)$ and N_0 are the angle averaged superconducting density of states and the normal density of states at the Fermi level, respectively. For an s-wave superconductor, when the temperature is lower than $0.5T_c$, the change in the penetration depth λ_L with respect to the zero temperature value is given by^[29]

$$\frac{\lambda(T)}{\lambda(0)} = 1 + \sqrt{\frac{\pi\Delta_0}{2k_B T}} \exp\left(-\frac{\Delta_0}{k_B T}\right), \quad (4)$$

where Δ is the zero temperature value of the superconducting energy gap, and k_B is the Boltzmann constant. One can immediately see that λ_L^{-2} should be nearly temperature independent at low temperatures ($T < 0.4T_c$) for a conventional s-wave superconductor,^[27] as shown by the dashed line in Fig. 1(b) which is distinct from our results. We therefore simulate our results by assuming two s-wave gaps, Δ_1 and Δ_2 . If the contribution to the superfluid density for Δ_1 is α , then it will be $1 - \alpha$ for Δ_2 . The total superfluid density n_{tot} is $\alpha n_{s1} + (1 - \alpha)n_{s2}$. From Eq. (3), the superfluid density can be further expressed as^[29]

$$\tilde{n}(T) = 1 + 2 \int_\Delta^\infty dE \frac{\partial f(E)}{\partial E} \frac{E}{\sqrt{E^2 - \Delta^2(T)}}. \quad (5)$$

By this way, we simulate the temperature dependence of Δf as shown in Fig. 1(b). The parameters $\Delta_1 = 1.2k_B T_c$, $\Delta_2 = 2.8k_B T_c$, and $\alpha = 0.85$ are obtained. The two-gaps feature in the superconducting state was also demonstrated by previous spin-lattice relaxation measurements,^[30] in which a ‘knee’ behavior was observed in temperature-dependent $1/T_1$. From the fitting by two s-wave gaps, $\Delta_1 = 1.3k_B T_c$ and $\Delta_2 = 3.0k_B T_c$ ^[30] are obtained, which are in good agreement with the present results. We also note that $\Delta_1 = 1.6k_B T_c$ of hole-like Fermi surfaces and $\Delta_2 = 2.3k_B T_c$ of electron-like Fermi surfaces were observed by a previous ARPES study in LiFeAs,^[31] which are also consistent with our results. Furthermore, the hole-like Fermi surfaces were found to be larger than the electron-like Fermi surfaces,^[31] which is in agreement with our simulation that α is larger than 0.5. This means that the main

contribution to the quasi-particles in the superconducting state is from the smaller superconducting energy gap Δ_1 that is of hole-like Fermi surfaces. Namely, the superconducting energy gap on hole-like Fermi surfaces is smaller than the gap on electron-like surfaces. This is in contrast to the situation in the BaFe₂As₂ family where the superconducting energy gap on hole-like Fermi surfaces is larger.^[9] It implies that the pairing mechanism in LiFeAs is indeed unique.^[32] More theoretical studies in this regard are needed in the future.

Figure 2(a) shows the temperature dependence of the resonance frequency of the NMR coil at various magnetic fields. The superconducting transition temperature T_c of the sample is found to be around 4.2 K at zero field, which is similar to an earlier report determined by DC susceptibility measurements.^[15] Figure 2(b) shows the NMR spectrum measured at $T = 4.2$ K by sweeping the magnetic field. We note that only one peak is observed for both ³¹P and ⁷Li nuclei. The total Hamiltonian for the nuclei with spin I can be expressed as^[33]

$$\mathcal{H} = \gamma \hbar I_z H_0 (1 + K) + \frac{e^2 q Q}{4I(2I - 1)} [3(I_z^2 - I^2)(3\cos^2\theta - 1)], \quad (6)$$

where K is the Knight shift, eq is the electric field gradient (EFG) along the principle axis z , Q is the nuclear quadrupole moment, and θ is the angle between the magnetic field and the principle axis of the EFG. For ³¹P with $I = 1/2$, only one peak is expected. For ⁷Li with $I = 3/2$, the NMR spectra should contain three lines. The fact that only one peak can be observed in our measurement is probably because the nuclear quadrupole moment Q of ⁷Li is very small^[34,35] and the central and satellite lines overlap.

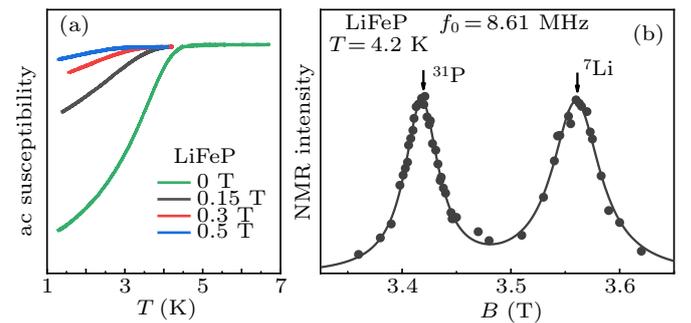


Fig. 2. (a) Temperature dependence of AC susceptibility of LiFeP at various fields. (b) NMR spectrum of LiFeP obtained by sweeping the magnetic fields at 4.2 K. The solid curve is fitted by two Lorentz functions.

Figure 3 shows the temperature dependence of ³¹P-NMR spectra at $B_0 = 0.15$ T. Similar to the observation in LiFeAs, a symmetric line broadening and a shift to the lower frequency below T_c are also observed in LiFeP. Above $T = 1.2$ K, we used a short pulse-repetition time in order to average the ³¹P signal as much times as possible. As a result, ⁷Li NMR signal is not seen, which has a long relaxation time. Below

$T = 1.2$ K, the spectrum was obtained by using a long pulse-repetition time in order to avoid heating the sample up. So a new peak is observed which is contributed from ^7Li nuclei as shown in Fig. 3. Since the FWHM of a convolution of two Gaussian functions is the quadratic sum of individual FWHMs, the broadening can be obtained as $\Delta f = \sqrt{(\text{FWHM}(T))^2 - (\text{FWHM}(T = T_c))^2}$.

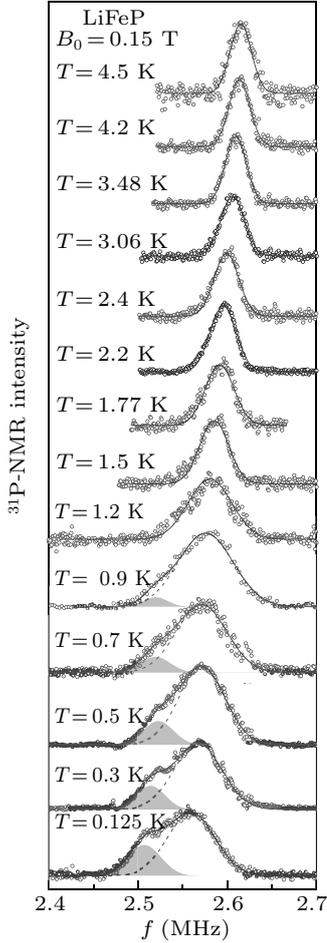


Fig. 3. (a) ^{31}P -NMR spectra of LiFeP at various temperatures with $B_0 = 0.15$ T. The spectra above $T = 1.2$ K are fitted by a single Gaussian function, while the spectra below $T = 1.2$ K are fitted by two Gaussian functions. The left peak (shaded area) is from ^7Li nuclei (see text for detail).

Figure 4 shows the temperature dependence of the line broadening Δf . We find that λ_L^{-2} , being proportional to Δf , increases continuously below T_c without any saturation down to the lowest temperature we have reached, $T = 0.125$ K $\sim 0.03 T_c$. Such temperature dependent behavior is in contrast to the observation in LiFeAs, which can be explained by the difference of the symmetry of the superconducting energy gap. If line nodes exist in the superconducting energy gap $\Delta(\mathbf{k})$, the density of states averaged over \mathbf{k} will increase linearly with energy. Therefore λ_L^{-2} should be proportional to T at low temperatures, which was observed by previous μSR measurements on clean polycrystalline samples of high- T_c cuprate superconductors.^[27] Figure 4 shows that the temperature de-

pendence of λ_L^{-2} is in good agreement with the theoretical calculation based on a d-wave model, as shown by the red line.^[36] Our results therefore indicate that there are nodes in the superconducting energy gap. We note though that our results do not mean that the superconducting gap of LiFeP has d-wave symmetry since the temperature dependence of λ_L^{-2} alone cannot discern d-wave symmetry from other nodal superconducting energy gap symmetries, such as circular line node observed in $\text{BaFe}_2(\text{As}_{0.7}\text{P}_{0.3})_2$.^[12]

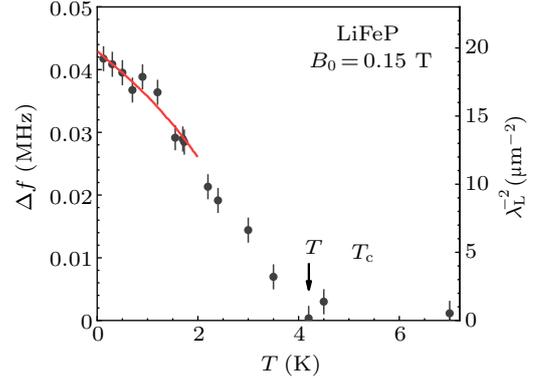


Fig. 4. Temperature-dependent line broadening Δf and the London penetration depth λ_L^{-2} of LiFeP. The red solid curve is the theoretical calculation based on a d-wave model.^[36]

3.2. Spin fluctuations in LiFeP

In most iron-pnictides, spin fluctuations have been observed in the normal state and considered as a possible glue for cooper pairs.^[11,20–22] However, in both LiFeP and LiFeAs, previous spin-lattice relaxation rate $1/T_1$ measurements show that spin correlations are rather weak.^[24,30] For LiFeAs, $1/T_1$ was measured at both zero and high fields,^[30,37] indicating that the spin correlations are indeed very weak at low energies. This is consistent with the ARPES study which shows that the electron and hole pockets are mismatched, leading to the bad nesting of the Fermi surfaces and then weak spin fluctuations.^[37] However, for LiFeP, $1/T_1$ was measured only at 4.65 T.^[24] In order to obtain the complete information about spin dynamics, we measure $1/T_1$ at various fields as shown in Fig. 5. At 7 T, the spin-lattice relaxation rate divided by temperature, $1/T_1 T$, is indeed nearly temperature independent. With decreasing field, $1/T_1 T$ starts to increase below $T \sim 10$ K. At 0.15 T, a strong enhancement of $1/T_1 T$ is clearly observed even in the superconducting state, indicating that spin correlations become much stronger at very low energies. In $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$, $1/T_1 T$ also shows an enhancement with cooling in the superconducting state, which is related to the spin glass transition.^[38] In such case, spin correlations should be further enhanced at higher magnetic fields due to the suppression of superconductivity. It means that $1/T_1 T$ should have a stronger temperature dependence at higher fields, in contrast to the observation in LiFeP.

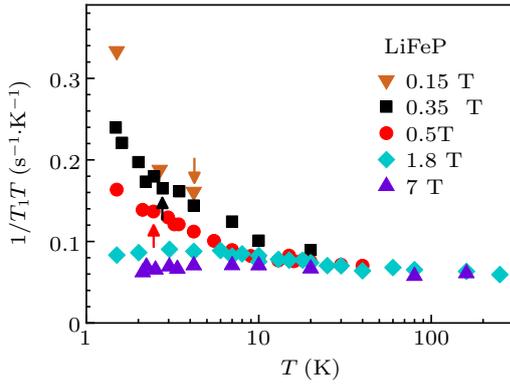


Fig. 5. Temperature evolution of $1/T_1T$ of LiFeP at various fields. The arrows mark the onsets of superconducting transition T_c under respective fields. The error bar for $1/T_1T$ is the s.d. in fitting the nuclear magnetization recovery curve and is smaller than the symbol size.

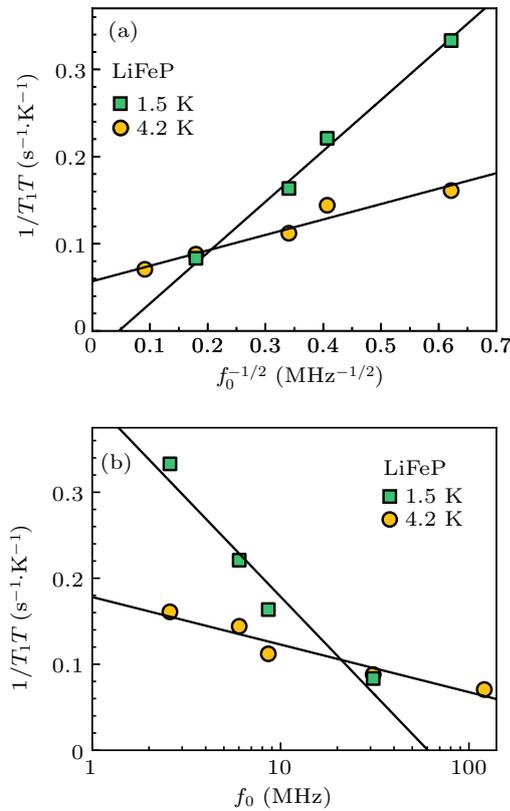


Fig. 6. (a) $1/T_1T$ as a function of $f_0^{-1/2}$. The solid curves are the linear fittings of $1/T_1T$ to $f_0^{-1/2}$. (b) $1/T_1T$ as a function of the NMR frequency f_0 . The solid curves indicate $1/T_1T \propto -\ln(f)$. The error bar is smaller than the symbol size.

In Fig. 6(a), we plot the value of $1/T_1T$ measured at 1.5 K and 4.2 K as a function of $f_0^{-1/2}$. The $1/T_1T$ appears to be proportional to $f_0^{-1/2}$, which is a typical behavior of the electronic spin diffusion in one-dimensional (1D) systems.^[39] The possibility of two-dimensional (2D) spin diffusion where $1/T_1T \propto -\ln(f)$ can not be fully excluded as shown in Fig. 6(b), although the fitting for 2D is not as good as the 1D situation. In a cuprate compound $Tl_2Ba_2CuO_y$, $1/T_1T \propto -\ln(f)$, which is related to 2D spin diffusion, was found above T_c .^[40] In any cases, our results clearly indicate that spin correlations in LiFeP have a diffusion characteristic,

meaning that the spin correlation function has an anomalously large contribution at long time. Similar behavior has also been observed in $La_{0.87}Ca_{0.13}FePO$, but only inside the superconducting state and was suggested to be originated from a spin-triplet symmetry of superconducting state.^[41,42] In our study, however, we find that the diffusive fluctuations exist far above T_c in the normal state of LiFeP, indicating that they are irrelevant to superconductivity. To the best of our knowledge, the nature of spin diffusion behavior in cuprate superconductors is still unclear, although this behavior has been discovered more than two decades. Thus we hope that our work will draw more theoretical attention for this issue.

4. Conclusion

In summary, we investigate the superconducting gap symmetry of LiFeP and LiFeAs by London penetration depth λ_L measurements. In LiFeAs, λ_L is found to saturate below $T \sim 0.2T_c$, meaning that the superconducting gap is fully opened. The temperature dependence of λ_L is analyzed by a two-gaps model and the two superconducting gaps of LiFeAs are acquired as $\Delta_1 = 1.2k_B T_c$ and $\Delta_2 = 2.8k_B T_c$. In contrast, we find that λ_L does not show any saturation with decreasing temperature down to $T \sim 0.03T_c$ in LiFeP. This indicates the existence of nodes in the superconducting energy gap function of LiFeP. Finally, we perform spin-lattice relaxation measurements at various fields in LiFeP. $1/T_1T$ is nearly temperature independent at 7 T, but is strongly enhanced at low fields below $T = 10$ K, suggesting that the spin correlation is enhanced at very low energies. We further find that $1/T_1T$ is proportional to $f^{-1/2}$, indicating that spin fluctuations have a 1D diffusive characteristic. Such behavior was also observed in some cuprate high- T_c superconductors, while its origin still needs more studies.

Acknowledgment

We thank S. Kawasaki and K. Matano for assistance in some of the measurements and helpful discussions.

References

- [1] Kamihara Y, Watanabe T, Hirano M and Hosono H 2008 *J. Am. Chem. Soc.* **130** 3296
- [2] Keimer B, Kivelson S A, Norman M R, Uchida S and Zaanen J 2015 *Nature* **518** 179
- [3] Dai P C 2015 *Rev. Mod. Phys.* **87** 855
- [4] Fernandes R M, Chubukov A V and Schmalian J 2014 *Nat. Phys.* **10** 97
- [5] Shen Z X, Dessau D S, Wells B O, King D M, Spicer W E, Arko A J, Marshall D, Lombardo L W, Kapitulnik A, Dickinson P, Doniach S, DiCarlo J, Loeser T and Park C H 1993 *Phys. Rev. Lett.* **70** 1553
- [6] Wollman D A, Van Harlingen D J, Lee W C, Ginsberg D M and Leggett A J 1993 *Phys. Rev. Lett.* **71** 2134
- [7] Matano K, Ren Z A, Dong X L, Sun L L, Zhao Z X and Zheng G Q 2008 *Europhys. Lett.* **83** 57001

- [8] Ding H, Richard P, Nakayama K, Sugawara K, Arakane T, Sekiba Y, Takayama A, Souma S, Sato T, Takahashi T, Wang Z, Dai X, Fang Z, Chen G F, Luo J L and Wang N L 2008 *Europhys. Lett.* **83** 47001
- [9] Li Z, Sun D L, Lin C T, Su Y H, Hu J P and Zheng G Q 2011 *Phys. Rev. B* **83** 140506
- [10] Ge Q Q, Ye Z R, Xu M, Zhang Y, Jiang J, Xie B P, Song Y, Zhang C L, Dai P C, and Feng D L 2013 *Phys. Rev. X* **3** 011020
- [11] Oka T, Li Z, Kawasaki S, Chen G F, Wang N L and Zheng G Q 2012 *Phys. Rev. Lett.* **108** 047001
- [12] Zhang Y, Ye Z R, Ge Q Q, Chen F, Jiang J, Xu M, Xie B P and Feng D L 2012 *Nat. Phys.* **8** 371
- [13] Yoshida T, Ideta S, Shimojima T, *et al.* 2014 *Sci. Rep.* **4** 7292
- [14] Kuroki K, Usui H, Onari S, Arita R, and Aoki H 2009 *Phys. Rev. B* **79** 224511
- [15] Deng Z, Wang X C, Liu Q Q, Zhang S J, Lv Y X, Zhu J L, Yu R C and Jin C Q 2009 *Europhys. Lett.* **87** 37004
- [16] Wang X C, Liu Q Q, Lv Y X, Gao W B, Yang L X, Yu R C, Li F Y and Jin C Q 2008 *Solid State Commun.* **148** 538
- [17] Hashimoto K, Kasahara S, Katsumata R, Mizukami Y, Yamashita M, Ikeda H., Terashima T, Carrington A, Matsuda Y and Shibauchi T 2012 *Phys. Rev. Lett.* **108** 047003
- [18] Oh S, Mounce A M, Lee J A, Halperin W P, Zhang C L, Carr S and Dai P C 2013 *Phys. Rev. B* **87** 174517
- [19] Wang C G, Li Z, Yang J, Xing L Y, Dai G Y, Wang X C, Jin C Q, Zhou R and Zheng G Q 2018 *Phys. Rev. Lett.* **121** 167004
- [20] Nakai Y, Iye T, Kitagawa S, Ishida K, Ikeda H, Kasahara S, Shishido H, Shibauchi T, Matsuda Y and Terashima T 2010 *Phys. Rev. Lett.* **105** 107003
- [21] Ning F L, Ahilan K, Imai T, Sefat A S, McGuire M A, Sales B C, Mandrus D, Cheng P, Shen B and Wen H H 2010 *Phys. Rev. Lett.* **104** 037001
- [22] Zhou R, Li Z, Yang J, Sun D L, Lin C T and Zheng G Q 2013 *Nat. Commun.* **4** 2265
- [23] Hashimoto K, Cho K, Shibauchi T, Kasahara S, Mizukami Y, Katsumata R, Tsuruhara Y, Terashima T, Ikeda H, Tanatar M A, Kitano H, Salovich N, Giannetta R W, Walmsley P, Carrington A, Prozorov R and Matsuda Y 2012 *Science* **336** 1554
- [24] Man H Y, Guo S L, Zhi G X, Gong X, Wang Q, Ding C, Jin Y K and Ning F L 2014 *Europhys. Lett.* **105** 67005
- [25] Brandt E H 1988 *Phys. Rev. B* **37** 2349(R)
- [26] Harshman D R, Brandt E H, Fiory A T, Inui M, Mitzi D B, Schneemeyer L F and Waszczak J V 1993 *Phys. Rev. B* **47** 2905
- [27] Sonier J E, Brewer J H and Kiefl R F 2000 *Rev. Mod. Phys.* **72**, 769
- [28] Inosov D S, White J S, Evtushinsky D V, Morozov I V, Cameron A, Stockert U, Zabolotnyy V B, Kim T K, Kordyuk A A, Borisenko S V, Forgan E M, Klingeler R, Park J T, Wurmehl S, Vasiliev A N, Behr G., Dewhurst C D and Hinkov V 2010 *Phys. Rev. Lett.* **104** 187001
- [29] Carrington A and Manzano F 2003 *Physica C: Superconductivity* **385** 205
- [30] Li Z, Ooe Y, Wang X C, Liu Q Q, Jin C Q, Ichioka M and Zheng G Q 2010 *J. Phys. Soc. Jpn.* **79** 083702
- [31] Borisenko S V, V. Zabolotnyy B, Evtushinsky D V, Kim T K, Morozov I V, Yaresko A N, Kordyuk A A, Behr G, Vasiliev A, Follath R and Büchner B 2010 *Phys. Rev. Lett.* **105** 067002
- [32] Li C, Dai G Y, Cai Y Q, Wang Y, Wang X C, Gao Q, Liu G D, Huang Y, Wang Q Y, Zhang F F, Zhang S J, Yang F, Wang Z M, Peng Q J, Xu Z Y, Jin C Q, Zhao L and Zhou X J 2020 *Chin. Phys. B* **29** 107402
- [33] Abragam A 1961 *The principles of nuclear magnetism* (Oxford university press) p. 217
- [34] Jeglič P, Potočnik A, Klanjšek M, Bobnar M, Jagodič M, Koch K, Rosner H, Margadonna S, Lv B, Guloy A M and Arčon D 2009 *Phys. Rev. B* **81** 140511
- [35] Ma L, Zhang J, Chen G F and Yu W Q 2010 *Phys. Rev. B* **82** 180501
- [36] Hirschfeld P J and Goldenfeld N 1993 *Phys. Rev. B* **48** 4219(R)
- [37] Dai Y M, Miao H, Xing L Y, Wang X C, Wang P S, Xiao H, Qian T, Richard P, Qiu X G, Yu W, Jin C Q, Wang Z, Johnson P D, Homes C C and Ding H 2015 *Phys. Rev. X* **5** 031035
- [38] Frachet M, Vinograd I, Zhou R, Benhabib S, Wu S, Mayaffre H, Krämer S, Ramakrishna S K, Reyes A P, Debray J, Kurosawa T, Momono N, Oda M, Komiya S, Ono S, Horio M, Chang J, Proust C, LeBoeuf D and Julien M H 2020 *Nat. Phys.* **16** 1064
- [39] Benner H and Boucher J P 1990 in *Magnetic Properties of Layered Transition Metal Compounds*, edited by de Jongh L J (Kluwer academic publishers) p. 323
- [40] Kambe S, Yasuoka H, Hayashi A and Ueda Y 2008 *Phys. Rev. Lett.* **73** 197
- [41] Nakai Y, Ishida K, Kamihara Y, Hirano M and Hosono H 2008 *Phys. Rev. Lett.* **101** 077006
- [42] Julien M H 2008 *J. Phys. Soc. Jpn.* **77** 125002